

Supramolecular “Double-Propeller” Dimers of Hexanuclear Cu^{II}/Ln^{III} Complexes: A {Cu₃Dy₃}₂ Single-Molecule Magnet**

Ghenadie Novitchi, Wolfgang Wernsdorfer, Liviu F. Chibotaru, Jean-Pierre Costes, Christopher E. Anson, and Annie K. Powell*

Building molecular organizations with controlled structure is an important point of interest in supramolecular chemistry and materials science.^[1] The major force to build a supramolecular architecture is determined by a number of factors: 1) coordination bonding,^[2] 2) versatile hydrogen-bonding interactions^[3] 3) π - π -stacking interactions,^[4] and 4) electrostatic interactions.^[5] Hydrogen-bonding and π interactions are frequently employed as driving forces to give well-defined supramolecular architectures.^[6] In recent years, a number of discrete, as well as extended, heterometallic 3d-4f architectural arrays have been made with metal-ligand building blocks assembled by appropriate organic polydentate ligands.^[7,8] It has been shown that apart from their fascinating metallo-supramolecular structures and their relevant insights into metal-directed self-assembly processes, these polymetallic species can display unique magnetic properties, which result from the assembly of paramagnetic metal ions by bridging ligands.

The design of new materials based on aromatic polycarboxylic acids such as benzene-1,3,5-tricarboxylic acid (trimesic acid) is currently an important research topic for the community of chemists and physicists.^[9] We report herein on the molecular structure, the supramolecular association, and unusual magnetic properties of the first examples of three-bladed propellers made with heterometallic compounds (Cu₃Ln₃, Ln = Gd, Tb, Dy), which result from the coordination of Cu-Ln entities with trimesic acid.

The reaction of 2-hydroxy-3-(hydroxymethyl)-5-methylbenzaldehyde^[10] with propylenediamine (2:1 molar ratio) in

methanol, followed by addition of Cu(OAc)₂·2H₂O, yielded the “compartmental complex ligand” CuL·H₂O (Scheme S1 in the Supporting Information). This complex possesses a flexible O₂O'₂ metal binding site (2-phenoxo- and 2-hydroxymethyl oxygen atoms), which could accommodate 4f ions. In addition, the terminal -OH groups can participate in the formation of hydrogen bonds. Dinuclear heterometallic complexes [LCuLn(NO₃)₃]₂·3.5 THF (**1**) (Ln^{III} = Gd (**1a**), Tb (**1b**), Dy (**1c**)) were synthesized by reaction of CuL·H₂O with Ln(NO₃)₃·6H₂O in THF. Reaction of these heterobinuclear complexes with trimesic acid in an acetone/THF (1:2 ratio) gave the hexanuclear compounds [(μ_3 -C₉H₃O₆){LCuLn(NO₃)₂}]₃·3 THF (**2**) (Ln^{III} = Gd (**2a**), Tb (**2b**), Dy (**2c**)).

The IR spectra of the three compounds **1** were essentially identical, not just in the lower wavenumber “fingerprint” region, but also in the higher wavenumber region corresponding to hydrogen-bonded O-H stretches, indicating that the three compounds are closely isostructural. The same is true of the spectra of the complexes **2** (see the Supporting Information). All the spectra show characteristic vibrations of the coordinated ligand, with the ν_{C-N} and $\nu(C_{Ph}-O)$ stretching vibrations observed at 1625–1622 cm⁻¹ and 1029–1033 cm⁻¹, respectively. Bands assigned to nitrate ions (for example, in **2c** $\nu_{as}(NO_2) = 1468$; $\nu_s(NO_2) = 1298$; $\nu(NO) = 1001$ cm⁻¹) are also present. The extent of separation of the two highest frequency bands (170 cm⁻¹) suggested a bidentate chelating mode of coordination for these anions.^[11] The supplementary strong bands at 1710 cm⁻¹ present in the IR spectra of the hexanuclear compound **2c** can be assigned to the $\nu_{as}(COO^-)$ vibration of the trimesate carboxylate groups in a monodentate coordination mode.

The structures of **1b** and **2c** were determined by single-crystal X-ray diffraction. The structure of **1b** consists of LCu^{II}Tb^{III} binuclear units (Figure 1 a) in which the metal ions are doubly bridged by the two phenoxo oxygen atoms. Cu1 is located in the inner N₂O₂ site of the Schiff base ligand (L²⁻); these four atoms form a distorted equatorial plane with the apical positions occupied by the oxygen atom of a THF molecule (Cu1–O14A = 2.460(8) Å) on one side and the oxygen atom of a nitrate ligand (Cu1–O5 = 2.522(4) Å) on the other side. This nitrate ligand is also chelated to Tb1, so that O5 provides a supplementary $\eta^2:\eta^1$ Cu–Tb bridge, while the two remaining nitrate anions simply chelate Tb1. The Cu1...Tb1 distance is 3.3216(6) Å and the dihedral angle between the Tb1–O1–O3 and Cu1–O1–O3 planes is 41.62(2)°. The Tb atom in **1b** is ten-coordinate, ligated by four oxygen atoms from the ligand, four oxygen atoms from two chelating nitrate anions, and two from the bridging $\eta^2:\eta^1$ nitrate anion; the Tb1–O bond lengths vary from 2.392(3) to

[*] Dr. G. Novitchi, Dr. C. E. Anson, Prof. Dr. A. K. Powell
Institut für Anorganische Chemie, Universität Karlsruhe
Engesserstrasse 15, 76128 Karlsruhe (Germany)
Fax: (+49) 721-608-8142
E-mail: powell@aoc.uni-karlsruhe.de

Dr. G. Novitchi
Institute of Chemistry, Academy of Sciences of Moldova (Moldova)
Prof. Dr. W. Wernsdorfer
Institut Néel, CNRS, Grenoble Cedex 9 (France)
Prof. Dr. L. F. Chibotaru
Division of Quantum and Physical Chemistry
Katholieke Universiteit Leuven (Belgium)
Dr. J.-P. Costes
Laboratoire de Chimie de Coordination du CNRS, Toulouse (France)

[**] This work was supported by the DFG Center for Functional Nanostructures and MAGMANet (Grant NMP3-CT-2005-515767). G.N. is grateful to the Alexander von Humboldt Foundation for financial support.

Supporting information for this article is available on the WWW under <http://dx.doi.org/10.1002/anie.200805176>.

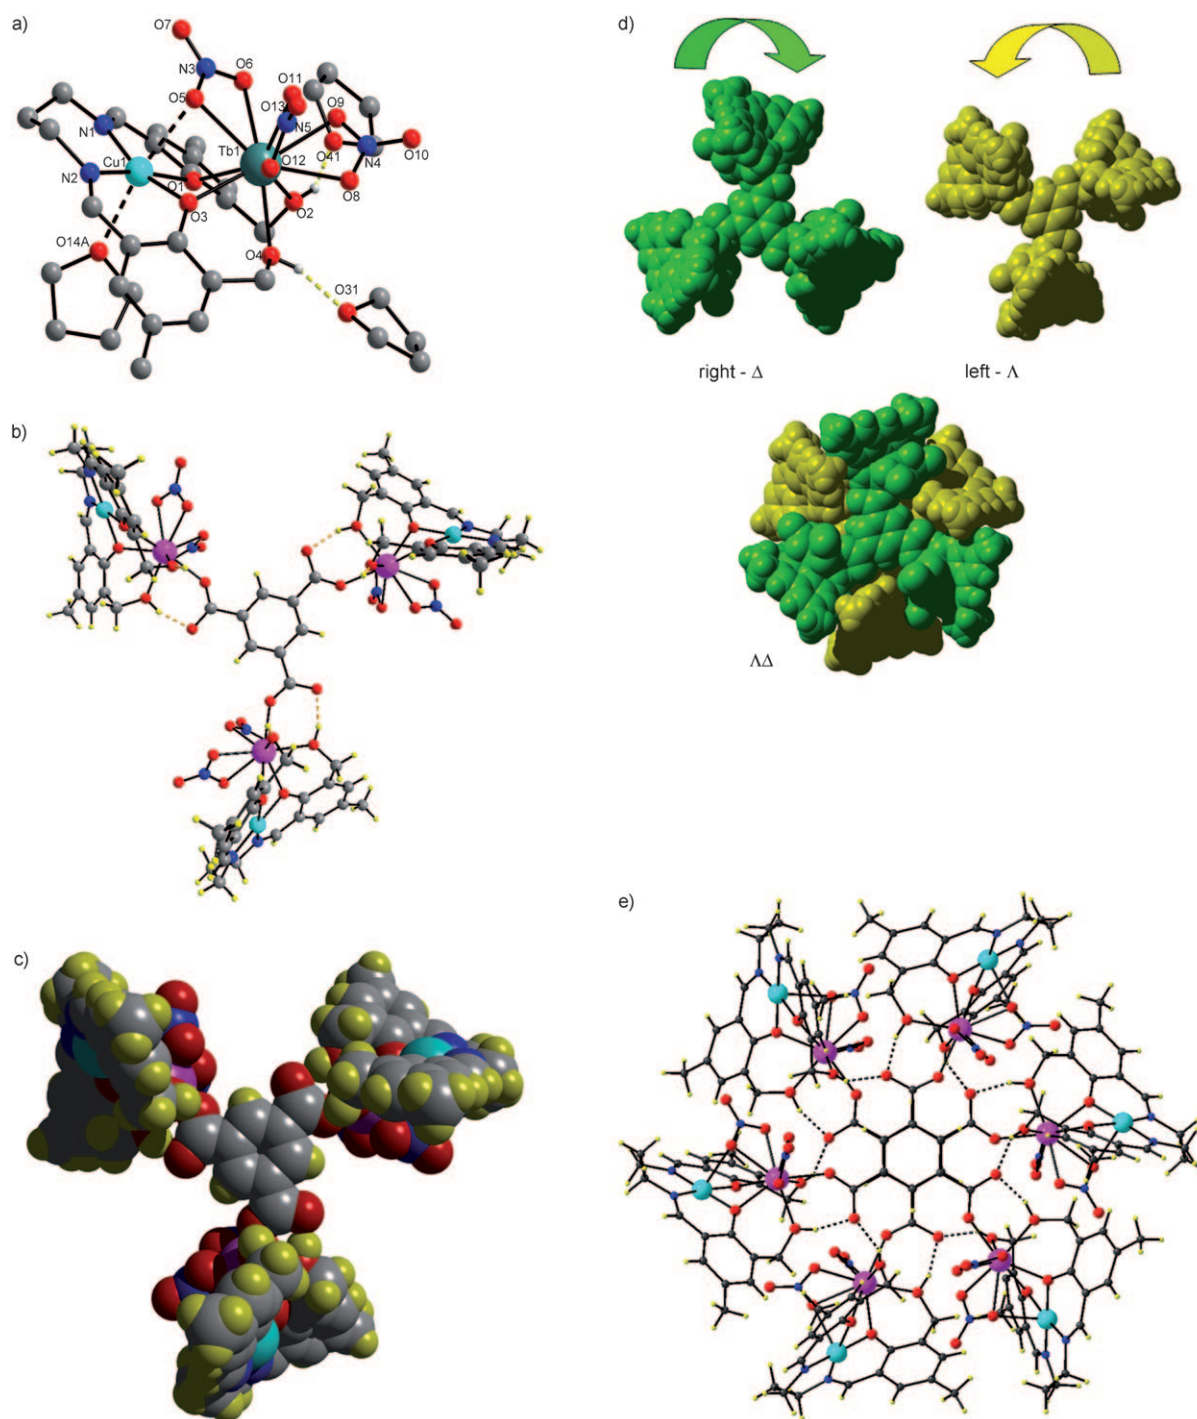


Figure 1. a) Molecular structure of complex **1b**; b) molecular structure of complex **2c**; c) space-filling model of complex **2c** (emphasizing the propeller structure); d) dodecanuclear supramolecular assembly of two hexanuclear heterometallic compounds (**2c**); e) **2c** viewed down the crystallographic *c* axis

2.539(3) Å. The two terminal OH groups of each LCu entity form strong hydrogen bonds with the oxygen atoms of two lattice THF molecules ($O4\cdots O31 = 2.664(6)$, $O2\cdots O41 = 2.671(6)$ Å). The structure of complex **2c**, which has threefold rotational site symmetry, is shown in Figure 1 b,c. Cu1 is five-coordinate and has an approximate square-pyramidal geometry. As for **1b**, the N_2O_2 atom set of the ligand defines the

equatorial plane of Cu1, and again an oxygen atom from a nitrate ligand that chelates Dy1 occupies an axial site ($Cu1-O5 = 2.501(8)$ Å). Cu1 and Dy1 are thus linked by two phenoxo bridges (O1 and O3), and O5 also forms a $\eta^2:\eta^1$ bridge with a $Cu\cdots Dy$ distance of 3.3035(15) Å.

The Dy^{III} ion is nine-coordinate with a capped square-antiprismatic geometry, and $Dy1-O$ bond lengths range from

2.320(2) to 2.558(2) Å. The coordination environment comprises four oxygen atoms from the two nitrate ligands, four oxygen atoms from the “compartmental complex ligand” (CuL) and one oxygen atom from the monodentate carboxylate ligand (Dy1–O11 = 2.312(2) Å). This last interaction is reinforced by a strong hydrogen bond from the Schiff base hydroxy oxygen atom O2 to the noncoordinated carboxylate oxygen atom O12. The CuO₂Dy core is again not planar, but has a dihedral angle between the Cu1–O1–O3 and Dy1–O1–O3 planes equal to 45.88(2)°. The trimesate ligand thus connects three binuclear [LCuDy(NO₃)₂] units to give a hexanuclear complex, resembling a three-bladed propeller, in which each blade is derived from a CuL moiety. The crystal site symmetry requires that all three blades have the same handedness (either left- (Λ) or right-handedness (Δ); Figure 1 d).

Pairs of hexanuclear compounds [(μ₃-C₉H₃O₆){LCuDy(NO₃)₂}]₂, related by a crystallographic $\bar{3}$ rotoinversion center, form a supramolecular assembly. The two molecules are linked by six intermolecular hydrogen bonds, each involving the second Schiff base hydroxy group O4 and a noncoordinated carboxylate oxygen atom from the second molecule. In addition, the aromatic rings of the two trimesate ligands are coparallel and their six carbon atoms are perfectly eclipsed, resulting in strong π–π stacking between the rings and separation between their planes of 3.543(4) Å (Figure 1 d,e), which strengthens the hexanuclear structure. Similar self-assembly by hydrogen bonds and π–π stacking has been found in a range of organic and coordination compounds,^[6] but this compound is the first example involving heterometallic CuLn units.

The magnetic behavior of **1a** and **2a** is shown in Figure S2 (in the Supporting Information) as a plot of $\chi_M T$ against T . At 300 K, $\chi_M T$ for **1a** is equal to 8.27 cm³ mol⁻¹ K, which corresponds to the value expected for two uncoupled Cu^{II} and Gd^{III} metal ions (8.25 cm³ mol⁻¹ K). Lowering the temperature causes $\chi_M T$ to increase to 8.94 cm³ mol⁻¹ K at 2 K, confirming the presence of a weak ferromagnetic Cu^{II}...Gd^{III} interaction. Compound **2a** shows a similar behavior. At 300 K, $\chi_M T$ for **2a** is 24.92 cm³ mol⁻¹ K, increasing slightly to 25.92 cm³ mol⁻¹ K at 2 K. As shown previously, 4f/4f magnetic interactions through carboxylate groups are very weak,^[12] and the interaction through the trimesate ligand will be even weaker. Quantitative analyses were performed for compounds **1a** and **2a** on the basis of classical Heisenberg–Dirac–van Vleck (HDVV) formalism derived from the isotropic Hamiltonian $H_d = -J \vec{S}_1 \vec{S}_2$.^[13] The data were fitted in the simultaneous $\chi_M T(T)$ and $\chi_M(T)$ thermal dependences including temperature-independent paramagnetism (TIP), impurity contribution (ρ), and intermolecular interaction (zJ) according to Equation (1) with $n = 1$ for **1a** and $n = 3$ for **2a**.

$$\chi_d = n \frac{4N\beta 15g_4^2 + 7g_3^2 \exp(-4J/kT)}{\kappa T (9 + 7 \exp(-4J/kT))} \quad (1)$$

The g values associated with the low lying levels $E(4) = 0$ and $E(3) = 4J$ are $g_4 = (7g_{Gd} + g_{Cu})/8$ and $g_3 = (9g_{Gd} - g_{Cu})/8$, respectively.^[13] Least-squares fitting of the experimental data

with g_{Gd} fixed at 2.00 led to the following sets of parameters: $g_{Cu} = 2.16(4)$ and $J = 0.20(4)$ cm⁻¹ for **1a**, and $g_{Cu} = 2.13(5)$ and $J = 0.11(4)$ cm⁻¹ for **2a**; agreement factors of $\Sigma(\chi T_{\text{calcd}} - \chi T_{\text{obsd}})^2 / \Sigma(\chi T_{\text{obsd}})^2$ are 2.5×10^{-4} and 3.5×10^{-4} , respectively. The experimental magnetization for **1a** and **2a** at 2.0 K are correctly fitted by Brillouin functions corresponding to coupled Cu^{II} and Gd^{III} ions (see the Supporting Information).

The interpretation of the magnetic data of complexes **1b**, **1c**, **2b**, and **2c** is not straightforward since the Tb^{III} and Dy^{III} ions possess first-order angular moments that preclude the use of spin-only Hamiltonians for isotropic exchange. The strong anisotropy of these ions leads to a deviation of the magnetic susceptibility from the Curie law, characterized by a decrease of the $\chi_M T$ product at low temperatures and the absence of saturation in the magnetization curves for **1b**, **1c**, **2b**, and **2c** (see the Supporting Information). If Cu–Tb or Cu–Dy interactions are active in these compounds, these must coexist alongside the above effect, and the resultant profiles of the $\chi_M T$ versus T curves are therefore not necessarily indicative of the sign of the magnetic interaction. Furthermore, we know from the study of the equivalent complexes **1a** and **2a** that the Cu–Ln interaction is weak. From the experimental results, we can tell that a weak ferromagnetic Cu–Tb interaction is present in **2b**. For the other three complexes, **1b**, **1c**, and **2c**, studies to lower temperature would be needed. Because of the weak values of the J parameters, the qualitative method, which consists of replacing the Cu ions by diamagnetic ones and comparing the $\chi_M T$ products of the two sets of complexes, is also unlikely to give a reliable answer.^[14b]

The ac susceptibility measurements for **2c** show frequency-dependent signals, suggesting single molecule magnetic (SMM) behavior. These are rather weak; the χ''/χ' ratios are low, and no maxima could be observed above 1.8 K for the out-of-phase signals. This low intensity is presumably due to population of low-lying excited states, which are a consequence of the weak magnetic interaction.

The magnetizations of single crystals of both **1c** {CuDy} and **2c** {Cu₃Dy₃}₂ as a function of applied field were studied with a micro-SQUID array in the 0.04–7 K range.^[15] For **1c**, the measurements at 0.04 K revealed hysteresis loops with a very low coercivity (Figure 2, top). Similar behavior was also found in other series of CuLn (Ln = Dy or Tb) compounds.^[16,17] By contrast, measurements on the supramolecularly associated {Cu₃Dy₃}₂ **2c**, for which the field was applied in the easy plane of the crystal, perpendicular to the threefold axis of the propeller, revealed hysteresis loops with a drastic increase in the coercivity relative to that of **1c**. The coercivity is dependent on both temperature and sweep rate (Figure 2, bottom), increasing with both decreasing temperature and increasing field sweep rate, as expected for SMM behavior, and is still large (ca. 0.5 T) above 1 K. The hysteresis loops also present a very large sweep-rate-independent step at zero field, which is due to quantum tunneling of the magnetization through the barrier.

The heterometallic dinuclear units in the case of **1** and **2** involve the same bicompartamental ligand. The coordination geometries about Cu and the lanthanide are similar in both

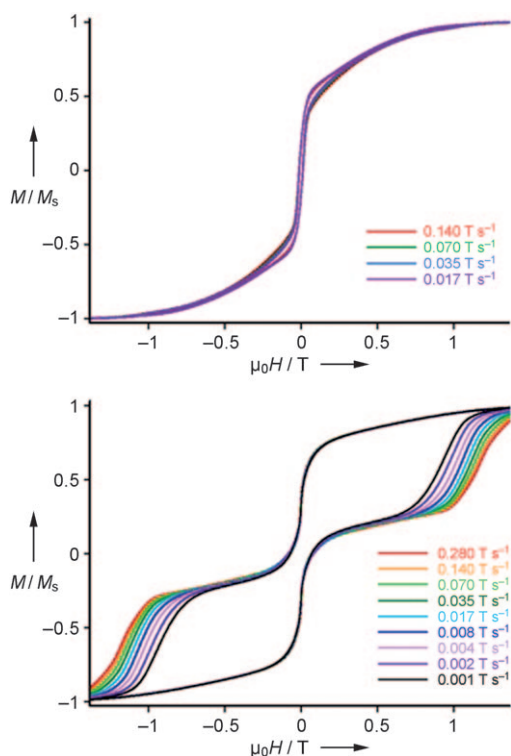


Figure 2. Single-crystal magnetization (M) versus applied field for complex **1c** $\{\text{CuDy}\}$ (top) and **2c** $\{\text{Cu}_3\text{Dy}_3\}_2$ (bottom) with different field sweep rates at 0.04 K. M is normalized to its saturation value at 1.4 T. For temperature-dependence data, see the Supporting Information.

cases. In particular, the CuO_2Ln dihedral angles, which determine the Cu-Ln magnetic interaction,^[14a] are very similar (see the Supporting Information), so we expect very similar intra- $\{\text{CuLn}\}$ behavior in **1c** and **2c**. Thus, to understand their strikingly different hysteretic behavior, we first note that it cannot be due to supramolecular magnetic interactions only, which are expected to be very weak in **2c** (of the order of tens of mK). Therefore, the observed magnetization steps basically originate from intradimer momentum reorientations, whereas the supramolecular interactions between the dimers are mainly responsible for the tunnel window^[18] for these transitions. In this respect, the situation is quite different from the case of the $[\{\text{Mn}_4\text{O}_3\text{Cl}_4(\text{O}_2\text{CET})_3\}_2]$ cluster, for which separation of magnetization steps along the field axis arises as a result of supramolecular magnetic interactions between the two Mn_4 units.^[19] The second observation is that in **1c** all $\{\text{CuDy}\}$ units (and their anisotropy axes) are parallel to each other, whereas in **2c** their magnetic axes form 120° in the ab plane for nearest neighbor ions (our ab initio calculations show that these axes essentially lie in the ab plane). Therefore the observed hysteresis in **2c** can be explained as follows: In a (quasi) axial ligand field the $^6\text{H}_{15/2}$ term of Dy^{III} ion splits into several well separated Kramers doublets, the ground one having a momentum projection close to $J=15/2$.^[20] The lowest energy levels of the CuDy dimer arise from the exchange interaction between the $S=1/2$ state of the Cu^{II} ion and the lowest Kramers doublet on the Dy^{III} site. Since the magnet-

ization curve for **1c** shows no activation behavior at low values of field, even at very low temperature (Figure 2), the exchange interaction is most probably of Ising type.

The reversal of magnetic moment on the Dy^{III} site, which is always directed along the anisotropy axis, can only be induced by the transverse components of the magnetic field, whereas the flipping rate is a very sensitive function of the amplitude of this field.^[18,21] In **1c** the applied field probably has a nonnegligible transverse component on the Dy^{III} ions in all of the CuDy units, which results in an almost completely adiabatic reversal of magnetization through resonance tunneling around the $H=0$ point and the lack of hysteresis. However, in **2c** the field applied in the ab plane will have different transverse components for the three Dy^{III} ions in the Cu_3Dy_3 units. It can eventually be oriented in such a way as to become almost parallel to the anisotropy axis of one of the Dy^{III} ions of the triangle (ions of type a in Figure 3). Then the transverse field on this ion will be small and the adiabatic channel of reversal of magnetization will be practically closed. In contrast, the field on the other two dysprosium sites (b and c in Figure 3) will make an angle of 60° with their anisotropy axes, giving rise to an adiabatic reversal of magnetization at any field sweep rates similar to the behavior of **1c**. At large

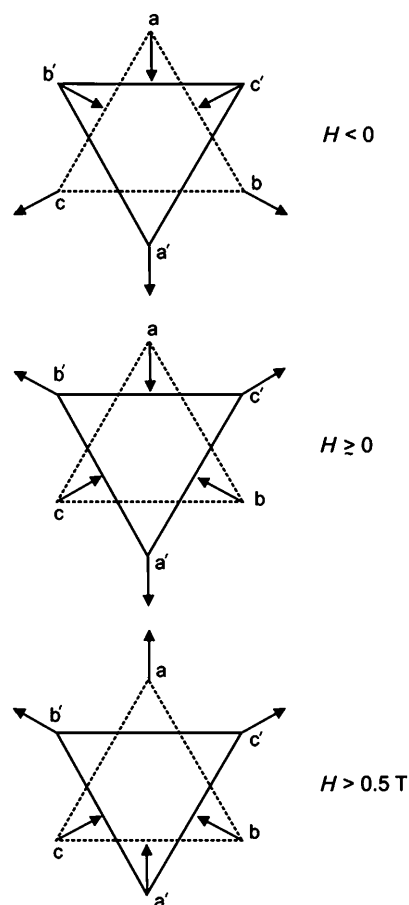


Figure 3. Evolution of the orientation of magnetic moments on the six dysprosium sites (arrows) of the double-propeller complex $\{\text{Cu}_3\text{Dy}_3\}_2$ with the magnetic field applied in the easy plane. Upper and lower dysprosium triangles are shown by solid and dashed lines, respectively.

negative fields, the magnetic moments on the Dy^{III} ions will be oriented as in the upper plot of Figure 3. Increasing the field up to $H \geq 0$ we cross the tunneling window, where adiabatic flips of magnetic moments on sites b and c occur (middle plot in Figure 3). Since the projection of their magnetic moments on the direction of the field is $1/2$, these flips will reduce the total magnetic moment to a value close to zero. At the same time the quantum tunneling of magnetization will not occur on dysprosium sites of type a, which instead will evolve nonadiabatically into the excited state when the field is swept to the positive region. Later on they will undergo thermal relaxation to the ground Zeeman component. This relaxation is associated with momentum reversal on these dysprosium sites (lowest plot in Figure 3), which will give rise to a second magnetization step (at $H > 0.5$ T in Figure 2), whose position will be dependent on the field sweep rate.

In conclusion, we present herein a supramolecular $\{Cu_3Dy_3\}_2$ compound in which the two hexanuclear complexes are associated by a combination of π - π -stacking interactions and hydrogen bonds. The linkage of the CuDy units, both intramolecular and supramolecular, appear to be responsible for reorientation of anisotropy axes on lanthanide ions and lead, therefore, to a drastic change in the SMM behavior.

Experimental Section

Experimental details of the synthesis and spectral characterization are presented in the Supporting Information.

Magnetic susceptibility data were collected on powdered samples with a Quantum Design MPMS SQUID magnetometer under a 0.1 T applied magnetic field. All data were corrected for diamagnetism of the ligands estimated from Pascal's constants.^[22]

X-ray analysis: The X-ray data were collected on Bruker SMART Apex (**1b**) and Stoe IPDS II (**2c**) diffractometers using graphite-monochromated Mo_{K α} radiation ($\lambda = 0.71073$ Å). Structures were solved by direct methods and refined against F_o^2 by using SHELXL-TL.^[23] Anisotropic displacement parameters were used for all ordered non-hydrogen atoms. The coordinates of hydrogen atoms bonded to oxygen atoms were refined; organic hydrogen atoms were placed in calculated positions. Restraints on geometries and thermal parameters were applied to disordered THF molecules. The structure of **2c** showed obverse/reverse twinning and was refined with data in HKLF 5 format.^[24]

1b: C₃₅H₅₂CuN₅O_{16.5}Tb (1029.28 g mol⁻¹); monoclinic, $P2_1/n$, $a = 10.6228(4)$, $b = 13.2409(5)$, $c = 29.6844(16)$ Å, $\beta = 99.177(1)^\circ$, $T = 100$ K, $Z = 4$, $V = 4121.8(3)$ Å³, $\rho_{\text{calcd}} = 1.659$ g cm⁻³, $F(000) = 2092$, $\mu(\text{MoK}\alpha) = 2.295$ mm⁻¹; 33736 data measured, of which 9406 unique ($R_{\text{int}} = 0.0322$); refinement (573/75 parameters) to $wR_2 = 0.1184$, $S = 1.073$ (all data), $R_1 = 0.0421$ (8058 data with $I > 2\sigma(I)$).

2c: C₈₄H₉₉Cu₃Dy₃N₁₂O₃₉ (2578.87 g mol⁻¹); trigonal, $R\bar{3}$, $a = 32.047(3)$, $c = 15.2776(17)$ Å, $T = 150$ K, $Z = 6$, $V = 13588(2)$ Å³, $\rho_{\text{calcd}} = 1.891$ g cm⁻³, $F(000) = 7704$, $\mu(\text{MoK}\alpha) = 3.235$ mm⁻¹. 30699 data measured, of which 6463 unique ($R_{\text{int}} = 0.1069$); refinement (433/32 parameters) to $wR_2 = 0.1906$, $S = 1.050$ (all data), $R_1 = 0.0756$ (4519 data with $I > 2\sigma(I)$).

CCDC 694351 (**1b**) and 694352 (**2c**) contain the supplementary crystallographic data for this paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data_request/cif

Received: October 22, 2008

Published online: January 20, 2009

Keywords: heterometallic compounds · magnetic properties · single molecule magnets · supramolecular chemistry

- [1] a) J.-M. Lehn, *Supramolecular Chemistry*, VCH, Weinheim, **1995**; b) J.-M. Lehn, *Struct. Bonding (Berlin)* **2000**, *96*, 3–29; c) G. M. Whitesides, B. Grzybowski, *Science* **2002**, *295*, 2418–2421; d) L. F. Lindoy, I. M. Atkinson, *Self-Assembly in Supramolecular Systems*, Royal Society of Chemistry, Cambridge, **2000**.
- [2] a) M. W. Hosseini, *Chem. Commun.* **2005**, 5825–5829; b) C. Janiak, *Dalton Trans.* **2003**, 2781; c) M. J. Zaworotko, *Chem. Commun.* **2001**, 1; d) E. B. Moulton, E. B. Rather, M. J. Zaworotko, *Cryst. Eng.* **2001**, *4*, 309; e) P. Losier, M. J. Zaworotko, *Angew. Chem.* **1996**, *108*, 2957; *Angew. Chem. Int. Ed. Engl.* **1996**, *35*, 2779.
- [3] a) M. W. Hosseini, *Coord. Chem. Rev.* **2003**, *240*, 157–166; b) H. W. Roesky, M. Andruh, *Coord. Chem. Rev.* **2003**, *236*, 91; c) T. Steiner, *Angew. Chem.* **2002**, *114*, 50; *Angew. Chem. Int. Ed.* **2002**, *41*, 48; d) M. R. Juan, B. Lee, *Coord. Chem. Rev.* **1999**, *183*, 43; e) T. N. Guru Row, *Coord. Chem. Rev.* **1999**, *183*, 81.
- [4] a) V. Russell, M. Scudder, I. Dance, *J. Chem. Soc. Dalton Trans.* **2001**, 798; b) C. J. Janiak, *Chem. Soc. Dalton Trans.* **2000**, 3885; c) I. Unamuno, J. M. Gutierrez-Zorrilla, A. Luque, P. Roman, L. Lezama, R. Calvo, T. Rojo, *Inorg. Chem.* **1998**, *37*, 6452; d) M.-C. Tse, K.-K. Cheung, M. C.-W. C.-M. Chan, *Chem. Commun.* **1998**, 3245.
- [5] a) P. D. Beer, P. A. Gale, *Angew. Chem.* **2001**, *113*, 502; *Angew. Chem. Int. Ed.* **2001**, *40*, 486; b) P. D. Beer, P. A. Gale, G. Z. Chen, *J. Chem. Soc. Dalton Trans.* **1999**, 1897; c) Y.-B. Dong, M. D. Smith, R. C. Layland, H.-C. zur Loye, *J. Chem. Soc. Dalton Trans.* **2000**, 775; d) D. S. Reddy, K. Panneerselvam, T. Pilati, G. R. Desiraju, *J. Chem. Soc. Chem. Commun.* **1993**, 661.
- [6] a) Y. Yashihito, M. Yoshizawa, M. Fujita, *J. Am. Chem. Soc.* **2008**, *130*, 5832–5833; b) T. Kato, N. Mizoshita, N. Kishimoto, *Angew. Chem.* **2006**, *118*, 44–74; *Angew. Chem. Int. Ed.* **2006**, *45*, 38–68; c) M. Yoshizawa, K. Kumazawa, M. Nagao, M. Kawano, T. Ozeki, M. Fujita, *Angew. Chem.* **2005**, *117*, 1844–1847; *Angew. Chem. Int. Ed.* **2005**, *44*, 1810–1813; d) M. L. Bushey, T.-Q. Nguyen, W. Zhang, D. Horoszewski, C. Nuckolls, *Angew. Chem.* **2004**, *116*, 5562–5570; *Angew. Chem. Int. Ed.* **2004**, *43*, 5446–5453; e) J. Van Gestel, A. R. A. Palmans, B. Titulaer, J. A. J. M. Vekemans, E. W. Meijer, *J. Am. Chem. Soc.* **2005**, *127*, 5490–5494.
- [7] a) M. Andruh, *Chem. Commun.* **2007**, 2565–2577; b) R. Gheorghe, P. Cucos, M. Andruh, J.-P. Costes, B. Donnadieu, S. Shova, *Chem. Eur. J.* **2006**, *12*, 187–203; c) C. D. Ene, F. Tuna, O. Fabelo, C. Ruiz-Perez, A. M. Madalan, H. W. Roesky, M. Andruh, *Polyhedron* **2008**, *27*, 574–582; d) R. Gheorghe, M. Andruh, J.-P. Costes, B. Donnadieu, M. Schmidtman, M. Achim, *Inorg. Chim. Acta* **2007**, *360*, 4044–4050; e) J. Kim, R. Banglin, M. Therese, H. Li, M. Eddaoudi, D. B. Moler, M. O'Keeffe, O. M. Yaghi, *J. Am. Chem. Soc.* **2001**, *123*, 8239–8247.
- [8] a) T. K. Prasad, M. V. Rajasekharan, J.-P. Costes, *Angew. Chem.* **2007**, *119*, 2909–2912; *Angew. Chem. Int. Ed.* **2007**, *46*, 2851–2854; b) G. Novitchi, J.-P. Costes, B. Donnadieu, *Eur. J. Inorg. Chem.* **2004**, 1808–1812; c) J.-P. Costes, G. Novitchi, S. Shova, F. Dahan, B. Donnadieu, J.-P. Tuchagues, *Inorg. Chem.* **2004**, *43*, 7792–7799; d) J.-P. Costes, J. M. Clemente-Juan, F. Dahan, J. Milon, *Inorg. Chem.* **2004**, *43*, 8200–8202.
- [9] a) C. Streb, D.-L. Long, L. Cronin, *Chem. Commun.* **2007**, 471–473; b) H. K. Chae, D. Y. Siberio-Perez, J. Kim, Y. B. Go, M. Eddaoudi, A. J. Matzger, M. O'Keeffe, O. M. Yaghi, *Nature* **2004**, *427*, 6974; c) B. Chen, M. Eddaoudi, S. T. Hyde, M. O'Keeffe, O. M. Yaghi, *Science* **2001**, *291*, 1021–1023; d) S.-B. Choi, M. J. Seo, M. Cho, Y. Kim, M. K. Jin, D.-Y. Jung, J.-S. Choi, E.-S. Ahn, J. L. C. Rowsell, J. Kim, *Cryst. Growth Des.* **2007**, *7*,

- 2290–2293; e) M. Eddaoudi, D. B. Moler, H. Li, B. Chen, T. M. Reineke, M. O’Keeffe, O. M. Yaghi, *Acc. Chem. Res.* **2001**, *34*, 319–330.
- [10] E. Lambert, B. Chabut, S. Chardon-Noblat, A. Deronzier, G. Chottard, A. Bousseksou, J.-P. Tuchagues, J. Laugier, M. Bardet, J.-M. Latour, *J. Am. Chem. Soc.* **1997**, *119*, 9424–9437.
- [11] K. Nakamoto, *Infrared and Raman Spectra of Inorganic and Coordination Compound*, 5th ed., Wiley, New York, **1997**.
- [12] a) J.-P. Costes, J. M. Clemente-Juan, F. Dahan, F. Nicodème, M. Verelst, *Angew. Chem.* **2002**, *114*, 333–335; *Angew. Chem. Int. Ed.* **2002**, *41*, 323–325; b) J.-P. Costes, F. Nicodème, *Chem. Eur. J.* **2002**, *8*, 3442–3447; c) M. Hernández-Molina, C. Ruiz-Perez, T. Lopez, F. Lioret, M. Julve, *Inorg. Chem.* **2003**, *42*, 5456–5458; d) D. John, W. Urland, *Eur. J. Inorg. Chem.* **2006**, 3503–3509; e) G. Abbas, Y. Lan, G. Kostakis, C. E. Anson, A. K. Powell, *Inorg. Chim. Acta* **2008**, *361*, 3494–3499.
- [13] a) M. L. Kahn, T. M. Rajendiran, Y. Jeannin, C. Mathoniere, O. Kahn, *C. R. Acad. Sci. Ser. IIc Chim.* **2000**, *3*, 131; b) G. Novitchi, S. Shova, A. Caneschi, J.-P. Costes, M. Gdaniec, N. Stanica, *Dalton Trans.* **2004**, 1194–1200; c) J.-P. Costes, F. Dahan, A. Dupuis, J.-P. Laurent, *Inorg. Chem.* **1996**, *35*, 2400.
- [14] a) J.-P. Costes, F. Dahan, A. Dupuis, *Inorg. Chem.* **2000**, *39*, 165–168; b) J.-P. Costes, F. Dahan, A. Dupuis, J.-P. Laurent, *Chem. Eur. J.* **1998**, *4*, 1616–1620.
- [15] W. Wernsdorfer, *Adv. Chem. Phys.* **2001**, *118*, 99.
- [16] a) C. Aronica, G. Pilet, G. Chastanet, W. Wernsdorfer, J.-F. Jacquot, D. Luneau, *Angew. Chem.* **2006**, *118*, 4775–4778; *Angew. Chem. Int. Ed.* **2006**, *45*, 4659–4662; b) T. Hamamatsu, K. Yabe, M. Towatari, S. Osa, N. Matsumoto, N. Re, A. Pochaba, J. J. Mrozinski, L. Gallani, A. Barla, P. Imperia, C. Paulsen, J.-P. Kappler, *Inorg. Chem.* **2007**, *46*, 4458–4468; c) F. Mori, T. Nyui, T. Ishida, T. Nogami, K.-Y. Choi, H. Nojiri, *J. Am. Chem. Soc.* **2006**, *128*, 1440–1441; d) S. Ueki, T. Ishida, T. Nogami, K.-Y. Choi, H. Nojiri, *Chem. Phys. Lett.* **2007**, *440*, 263.
- [17] a) J.-P. Costes, S. Shova, W. Wernsdorfer, *Dalton Trans.* **2008**, 1843–1849; b) Gh. Novitchi, J.-P. Costes, J.-P. Tuchagues, L. Vendier, W. Wernsdorfer, *New J. Chem.* **2008**, *32*, 197–200; c) J.-P. Costes, M. Auchel, F. Dahan, V. Peyrou, S. Shova, W. Wernsdorfer, *Inorg. Chem.* **2006**, *45*, 1924–1934; d) J.-P. Costes, F. Dahan, W. Wernsdorfer, *Inorg. Chem.* **2006**, *45*, 5–7; e) J.-P. Costes, J. M. Clemente-Juan, F. Dahan, J. Milon, *Inorg. Chem.* **2004**, *43*, 8200–8202.
- [18] B. Barbara, *Inorg. Chim. Acta* **2008**, *361*, 3371–3379; N. V. Prokofev, P. C. E. Stamp, *J. Phys. Condens. Matter* **1993**, *5*, L663–L670.
- [19] a) W. Wernsdorfer, N. Aliaga-Alcalde, D. N. Hendrickson, G. Christou, *Nature* **2002**, *416*, 406–409; b) S. Hill, R. S. Edwards, N. Aliaga-Alcalde, G. Christou, *Science* **2003**, *302*, 1015–1018.
- [20] L. F. Chibotaru, L. Ungur, A. Soncini, *Angew. Chem.* **2008**, *120*, 4194–4197; *Angew. Chem. Int. Ed.* **2008**, *47*, 4126–4129.
- [21] D. Gatteschi, R. Sessoli, *Angew. Chem.* **2003**, *115*, 278–309; *Angew. Chem. Int. Ed.* **2003**, *42*, 268–297.
- [22] P. Pascal, *Ann. Chim. Phys.* **1910**, *19*, 5.
- [23] G. M. Sheldrick, SHELXTL 6.12, Bruker AXS Inc., Madison, **2003**.
- [24] R. Herbst-Imer, G. M. Sheldrick, *Acta Crystallogr. Sect. B* **2002**, *58*, 477–481.